

深圳市恒昌泰科技有限公司

深圳市宝安区松岗街道立业路兆丰祥商务大厦 1209-1210 号房 (办公场所)

样品描述 : BPP
 材料类型 : 聚丙烯
 材料成分 : PP
 型号 : JJ2100(+)

到样日期 : 2023年06月01日
 测试周期 : 2023年06月01日至2023年07月14日

测试项目	PAS 9017 测试要求	样品	结论
聚烯烃产品类别	附录 B	聚丙烯+生物降解助剂	/
羰基指数	>1	1.16	符合
数均分子量 (Mn)	<5000 Da	2907	符合
Z 均分子量 (Mz)	<30000 Da	21430	符合
重均分子量 (Mw) 损失百分比%	>90%	98	符合
幼苗出苗和幼苗生长试验 1	OECD 208		有效
大型溞繁殖试验 1	OECD 211		有效
蚯蚓繁殖试验 1	OECD 222		有效
土壤生物降解测试 2	>90%	99.4%	符合

备注:

1. 测试结果符合 OECD 208, 222 和 211 标准的生态毒性要求, 测试在 RECETOX 完成, 详见报告后附的生态毒性声明文件, 该声明文件遵循 PAS9017 相关要求。
2. 测试结果符合 PAS9017 相关要求, 依据 ISO 17556 方法并在 AIMPLAS 完成测试, 测试样品在 278 天内实现了 99.4% 的生物降解。测试数据详见附件“AIMPLAS 报告 AIMPLAS report AST-21-097-06”。
3. GB/T 22047-2008 等同采用 ISO 17556-2003《土壤中塑料材料最终需氧生物分解能力的测定通过测定密闭呼吸计中需氧量或测定释放的二氧化碳的方法》, 技术性内容完全相同。

通标标准技术服务(上海)有限公司
 授权代表签署

张海宁

扫码查看在线报告



SHHL2305025627SD

张海宁
 授权签字人



除非另有书面协议, 本报告由本公司依据《服务通用条款》出具。
 《服务通用条款》印刷在正本报告纸背面, 或通过 <http://www.sgs.com/en/Terms-and-Conditions.aspx> 查询, 电子格式文件可通过 <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx> 获取, 请特别关注其中涉及责任限制、赔偿以及司法管辖的相关条款。任何报告的持有方需知悉, 此报告内容仅反映SGS受限于客户指示下, 且在当时所得结论。SGS仅对其客户负责, 并且此报告不能免除交易各方根据交易文件所享有的权利和应履行的义务。未获得本公司书面批准, 本文件不得进行复制, 全文除外。任何未经授权对报告内容及形式进行的修改、伪造或扭曲都是违法行为, 违法者将会被追究法律责任。除非另有声明, 本测试报告所示结果仅涉及受测试样品, 此样品只保留30天。
 Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com
 4th Building, No.889, Yishan Road, Xuhui District Shanghai, China 200233 t (86) 400 960 9661 f (86-21) 6115 6899 www.sgsgroup.com.cn
 中国·上海·徐汇区宜山路889号4号楼 邮编: 200233 t (86) 400 960 9661 f (86-21) 6115 6899 sgs.china@sgs.com

详情如下:

测试项目	报告编号	发布日期	实验室名称	测试标准	测试结果
土壤生物降解测试	AST-21-097-06	07/02/2023	AIMPLAS	ISO 17556	有效

测试步骤:

氙灯老化测试参数应符合 PAS 9017: 2020 规定, 参考 ASTM D2565-16 或 BS EN ISO 4892-2。

测试条件:

辐照度: (0.35 ± 0.02) W / $(m^2 \cdot nm)$ @340nm

光照: 8h, 黑标温度 (73 ± 2) °C, 箱体温度 (60 ± 2) °C, 相对湿度 (50 ± 5) %

黑暗: 16h, 箱体温度 (60 ± 2) °C, 相对湿度 (50 ± 5) %

滤镜: Daylight-B/B

暴露时间: 672h

采样频率:

采样频率以小时计, 与氙灯老化设备的测试时间有关。见下表。

每个采样间隔, 从氙灯老化设备中取出一个样品并放入袋子中, 用来进行后续分析。装有样品的袋子上应贴上包含样品 ID 和采样时间信息的标签。

频率 (小时)	材料
	聚丙烯
0	红外 & 凝胶渗透色谱
168	红外
336	红外
504	红外
672	红外 & 凝胶渗透色谱



除非另有书面协议, 本报告由本公司依据《服务通用条款》出具。
 《服务通用条款》印刷在正本报告纸背面, 或通过 <http://www.sgs.com/en/Terms-and-Conditions.aspx> 查询, 电子格式文件可通过 <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx> 获取, 请特别关注其中涉及责任限定、赔偿以及司法管辖的相关条款。任何报告的持有方需知悉, 此报告内容仅反映SGS受限于客户指示下, 且在当时所得结论。
 SGS仅对其客户负责, 并且此报告不能免除交易各方根据交易文件所享有的权利和应履行的义务。未获得本公司书面批准, 本文件不得进行复制, 全文除外。任何未经授权对报告内容及形式进行的修改、伪造或扭曲都是违法行为, 违法者将会被追究法律责任。除非另有声明, 本测试报告所示结果仅涉及受测试样品, 此样品只保留30天。
 Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com
 4th Building, No.889, Yishan Road, Xuhui District Shanghai, China 200233 t (86) 400 960 9661 f (86-21) 6115 6899 www.sgs.com.cn
 中国·上海·徐汇区宜山路889号4号楼 邮编: 200233 t (86) 400 960 9661 f (86-21) 6115 6899 sgs.china@sgs.com

样品分析:

1. 傅立叶红外

配备衰减全反射 (ATR) 附件的 Thermo Nicolet IS10 FTIR, 用于样品的红外分析。

ATR 是一种与红外光谱结合使用的采样技术, 可以直接在固态或液态下检查样品而无需进一步制备, 可在预处理后立即对样品进行测试。FTIR 设备每年由赛默飞世尔工程师进行校准、维修和维护。每种材料、每个采样时间点测试三个平行样。FTIR 测试参数如下:

- 波数范围: 550 cm^{-1} 至 4000 cm^{-1}
- 扫描分辨率: 4 cm^{-1}
- 扫描次数: 32 次
- 后台扫描次数: 每次采样前 32 次

根据 FTIR 测试中采集的光谱, 羰基峰, 并计算羰基指数, 羰基指数 CI 计算方式如下:

$$\text{羰基指数} = \frac{\text{波数 } 1714 \text{ cm}^{-1} \text{ 周围的羰基峰面积}}{\text{波数 } 1470 \text{ cm}^{-1} \text{ 周围的 } \text{CH}_2 \text{ 剪刀峰面积}}$$

在计算羰基指数时, 使用以下峰区域:

羰基峰: 1650 cm^{-1} to 1850 cm^{-1}

CH_2 峰: 1420 cm^{-1} to 1500 cm^{-1}

2. 凝胶渗透色谱

通过将 10 mL 溶剂加入 20 mg 样品来制备溶液, 将制备的溶液加热并在 160°C 下震荡 4 小时, 或直至样品溶解。将试样放置在自动进样器中, 自动进样每个小瓶的部分内容物。本节中的所有质量、体积、时间和温度都只是近似值。

- 仪器: 安捷伦 PL GPC220
- 色谱柱: PLgel Olexis
- 溶剂 μm : 1, 2, 4-三氯苯
- 流速: 1.0 毫升/分钟
- 温度: 160°C
- 检测器: RI

数据采集和后续数据处理均使用安捷伦科技公司的“Cirrus”软件进行。

GPC 系统使用一系列已知分子量的安捷伦/聚合物实验室 EasiVial PS-H 聚苯乙烯标准品进行校准, 应用 Mark-Houwink 参数校正线性聚乙烯或聚丙烯均聚物的结果 (使用的 Mark Houwink 参数见下表)。

Mark Houwink 参数	聚苯乙烯 (标准品)	聚丙烯
Alpha	0.65	0.725
$K \times 10^{-5} \text{ dL/g}$	19	19

样品是完全可溶的。溶液过滤或色谱都没有明显的问题。



除非另有书面协议, 本报告由本公司依据《服务通用条款》出具。
 《服务通用条款》印刷在正本报告纸背面, 或通过 <http://www.sgs.com/en/Terms-and-Conditions.aspx> 查询, 电子格式文件可通过 <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx> 获取, 请特别关注其中涉及责任限制、赔偿以及司法管辖的相关条款。任何报告的持有方需知悉, 此报告内容仅反映SGS受限于客户指示下, 且在当时所得结论。SGS仅对其客户负责, 并且此报告不能免除交易各方根据交易文件所享有的权利和应履行的义务。未获得本公司书面批准, 本文件不得进行复制, 全文除外。任何未经授权对报告内容及形式进行的修改、伪造或扭曲都是违法行为, 违法者将会被追究法律责任。除非另有声明, 本测试报告所示结果仅涉及受测试样品, 此样品只保留30天。
 Attention: To check the authenticity of testing/inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com
 4th Building, No.889, Yishan Road, Xuhui District Shanghai, China 200233 t (86) 400 960 9661 f (86-21) 6115 6899 www.sgs.com.cn
 中国·上海·徐汇区宜山路889号4号楼 邮编: 200233 t (86) 400 960 9661 f (86-21) 6115 6899 sgs.china@sgs.com

测试结果:

1. 羰基指数均值 (CI)

样品	氙灯光老化后羰基指数均值 (CI)				
	0h	168h	336h	504h	672h
聚丙烯	0.01	0.60	1.36	1.31	1.16
标准方差	0.01	0.05	0.09	0.18	0.07

附录 - 红外测试数据

		聚丙烯		羰基指数 (CI)
		峰面积	峰面积	
		1850-1650 cm ⁻¹	1500-1420 cm ⁻¹	
初始样品	1	0.02	2.01	0.01
	2	0.04	3.81	0.01
	3	0.00	2.25	0.00
	均值	0.02	2.69	0.01
	标准方差	0.02	0.98	0.01
氙灯老化 168h	1	2.16	3.84	0.56
	2	2.58	3.90	0.66
	3	2.13	3.67	0.58
	均值	2.29	3.80	0.60
	标准方差	0.25	0.12	0.05
氙灯老化 336h	1	2.10	1.68	1.25
	2	3.41	2.46	1.39
	3	3.72	2.60	1.43
	均值	3.08	2.25	1.36
	标准方差	0.86	0.50	0.09
氙灯老化 504h	1	4.17	3.06	1.36
	2	4.02	2.75	1.46
	3	2.36	2.13	1.11
	均值	3.52	2.65	1.31
	标准方差	1.00	0.47	0.18
氙灯老化 672h	1	3.70	3.07	1.21
	2	3.51	2.94	1.19
	3	1.85	1.72	1.08
	均值	3.02	2.58	1.16
	标准方差	1.02	0.74	0.07

2. 分子量测试

	Mw 初始	Mw 672h	Mn 初始	Mn 672h	Mz 初始	Mz 672h	Mw 损耗率 (%)	Mw/Mn(PD) 初始	Mw/Mn(PD) 672h
聚丙烯	258066	8198	72735	2907	597150	21430	98%	3.5480	2.8201
标准方差	5823	130	7780	155	24106	752	/	/	/



除非另有书面协议, 本报告由本公司依据《服务通用条款》出具。
 《服务通用条款》印刷在正本报告纸背面, 或通过 <http://www.sgs.com/en/Terms-and-Conditions.aspx> 查询, 电子格式文件可通过 <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx> 获取。请特别关注其中涉及责任限定, 赔偿以及司法管辖的相关条款。任何报告的持有方需知悉, 此报告内容仅反映SGS受限于客户指示下, 且在当时所得结论。SGS仅对其客户负责, 并且此报告不能免除交易各方根据交易文件所享有的权利和应履行的义务。未获得本公司书面批准, 本文件不得进行复制, 全文除外。任何未经授权对报告内容及形式进行的修改、伪造或扭曲都是违法行为, 违法者将会被追究法律责任。除非另有声明, 本测试报告所示结果仅涉及受测试样品, 此样品只保留30天。
 Attention: To check the authenticity of testing/inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN_Doccheck@sgs.com
 4th Building, No.889, Yishan Road, Xuhui District Shanghai, China 200233 t (86) 400 960 9661 f (86-21) 6115 6899 www.sgs.com.cn
 中国·上海·徐汇区宜山路889号4号楼 邮编: 200233 t (86) 400 960 9661 f (86-21) 6115 6899 sgs.china@sgs.com

备注:

Mw: 重均分子量; Mn: 数均分子量; Mz: Z均分子量

附录 - 凝胶渗透色谱测试数据


条件		聚丙烯
Mw, 初始样品	1	261644
	2	261207
	3	251347
	均值	258066
	标准方差	5823
Mw, 672h 氙灯老化	1	8344
	2	8095
	3	8154
	均值	8198
	标准方差	130
Mn, 初始样品	1	66722
	2	81521
	3	69961
	均值	72735
	标准方差	7780
Mn, 672h 氙灯老化	1	3007
	2	2871
	3	2773
	均值	2907
	标准方差	155
Mz, 初始样品	1	624380
	2	578537
	3	588533
	均值	597150
	标准方差	24106
Mz, 672h 氙灯老化	1	21086
	2	20912
	3	22292
	均值	21430
	标准方差	752

备注: GPC测试分包广州特种承压设备检验研究所





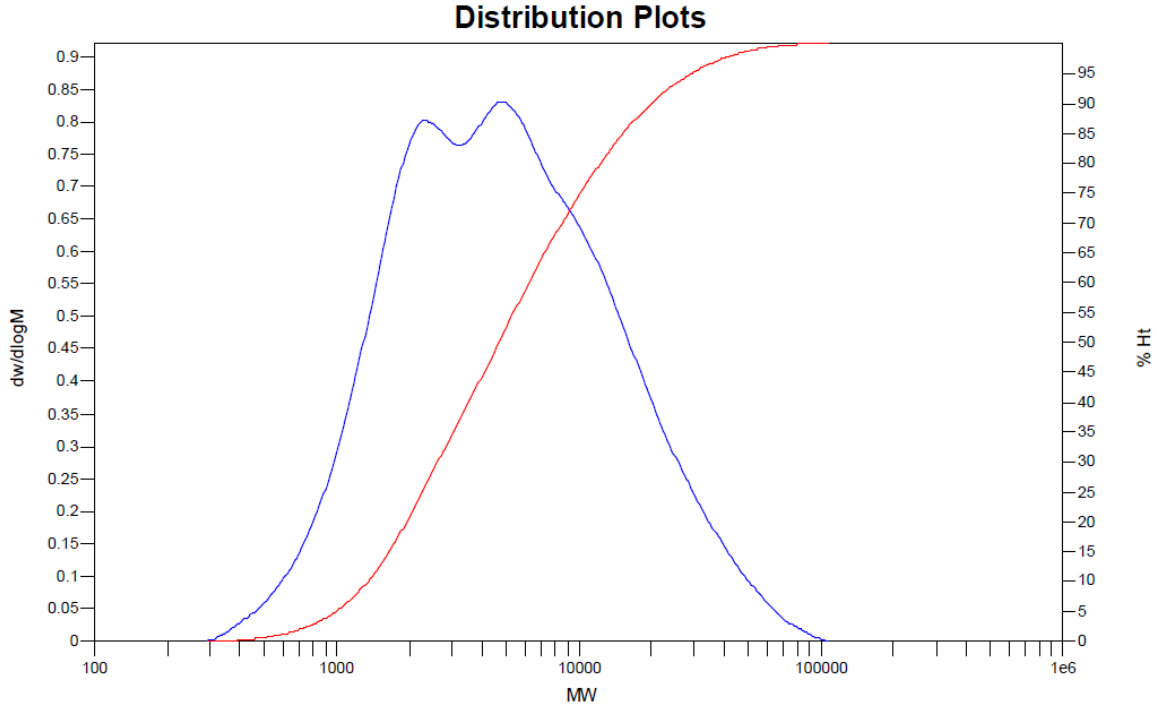


除非另有书面协议, 本报告由本公司依据《服务通用条款》出具。
 《服务通用条款》印刷在正本报告纸背面, 或通过 <http://www.sgs.com/en/Terms-and-Conditions.aspx> 查询, 电子格式文件可通过 <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx> 获取。请特别关注其中涉及责任限定, 赔偿以及司法管辖的相关条款。任何报告的持有方需知悉, 此报告内容仅反映SGS受限于客户指示下, 且在当时所得结论。SGS仅对其客户负责, 并且此报告不能免除交易各方根据交易文件所享有的权利和应履行的义务。未获得本公司书面批准, 本文件不得进行复制, 全文除外。任何未经授权对报告内容及形式进行的修改、伪造或扭曲都是违法行为, 违法者将会被追究法律责任。除非另有声明, 本测试报告所示结果仅涉及受测试样品, 此样品只保留30天。
 Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN_Doccheck@sgs.com
 4th Building, No.889, Yishan Road, Xuhui District Shanghai, China 200233 t (86) 400 960 9661 f (86-21) 6115 6899 www.sgs.com.cn
 中国·上海·徐汇区宜山路889号4号楼 邮编: 200233 t (86) 400 960 9661 f (86-21) 6115 6899 sgs.china@sgs.com

GPC分布图:



除非另有书面协议, 本报告由本公司依据《服务通用条款》出具。
 《服务通用条款》印刷在正本报告纸背面, 或通过 <http://www.sgs.com/en/Terms-and-Conditions.aspx> 查询, 电子格式文件可通过 <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx> 获取。请特别关注其中涉及责任限定, 赔偿以及司法管辖的相关条款。任何报告的持有方需知悉, 此报告内容仅反映SGS受限于客户指示下, 且在当时所得结论。SGS仅对其客户负责, 并且此报告不能免除交易各方根据交易文件所享有的权利和应履行的义务。未获得本公司书面批准, 本文件不得进行复制, 全文除外。任何未经授权对报告内容及形式进行的修改、伪造或扭曲都是违法行为, 违法者将会被追究法律责任。除非另有声明, 本测试报告所示结果仅涉及受测试样品, 此样品只保留30天。
 Attention: To check the authenticity of testing /inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com
 4th Building, No.889, Yishan Road, Xuhui District Shanghai, China 200233 t (86) 400 960 9661 f (86-21) 6115 6899 www.sgs.com.cn
 中国·上海·徐汇区宜山路889号4号楼 邮编: 200233 t (86) 400 960 9661 f (86-21) 6115 6899 sgs.china@sgs.com

测试样品:

	
原样	氙灯老化 168 小时
	
氙灯老化 336 小时	氙灯老化 504 小时
	/
氙灯老化 672 小时	/



除非另有书面协议, 本报告由本公司依据《服务通用条款》出具。

《服务通用条款》印刷在正本报告纸背面, 或通过 <http://www.sgs.com/en/Terms-and-Conditions.aspx> 查询, 电子格式文件可通过 <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx> 获取。请特别关注其中涉及责任限定, 赔偿以及司法管辖的相关条款。任何报告的持有方需知悉, 此报告内容仅反映SGS受限于客户指示下, 且在当时所得结论。SGS仅对其客户负责, 并且此报告不能免除交易各方根据交易文件所享有的权利和应履行的义务。未获得本公司书面批准, 本文件不得进行复制, 全文除外。任何未经授权对报告内容及形式进行的修改、伪造或扭曲都是违法行为, 违法者将会被追究法律责任。除非另有声明, 本测试报告所示结果仅涉及受测试样品, 此样品只保留30天。

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com
 4th Building, No.889, Yishan Road, Xuhui District Shanghai, China 200233 t (86) 400 960 9661 f (86-21) 6115 6899 www.sgsgroup.com.cn
 中国·上海·徐汇区宜山路889号4号楼 邮编: 200233 t (86) 400 960 9661 f (86-21) 6115 6899 sgs.china@sgs.com



Ecotoxicity Statement

This statement confirms that plastic products biotransformed by Polymateria's additive technologies, specified hereunder, have met all ecotoxicity criteria set out by BS PAS 9017:2020 for:

- Freshwater aquatic and;
- Soil invertebrates and;
- Plant eco-toxicity

And can thus be considered safe for contact in these environments.

The testing and reporting were conducted at RECETOX, a third-party laboratory ISO17025:2005 accredited for chemical trace analysis and conducting the research, development and utilization of environmental eco-toxicity testing.

Persons responsible for the ecotoxicological testing and reporting – Mgr. Jana Vašíčková, Ph.D. & Mgr. Marek Šudoma, Ph.D.

Study dates: 22nd December 2020 - 20th February 2021




Place of study - Research Centre for Toxic Compound in the Environment (RECETOX), Faculty of Science, Masaryk University, Brno, Czech Republic.

Biotransformed products in study:

Sample ID	Description of the material tested	PAS 9017 Annex B category
Product 8	Plastic bottle (PP) containing Masterbatch formulation No. 1 of Cycle+	Polypropylene (+ BA)
Product 9	Plastic film (PE) containing Masterbatch formulation No. 1 of Cycle+	Polyethylene (+ BA)

Biotransformed products met criteria for:

- Chronic toxicity:

OECD 208	OECD 211	OECD 222
		
Terrestrial plants	<i>Daphnia</i> sp.	Earthworm

OECD 208: Terrestrial plant test (*Sinapis alba* and *Hordeum vulgare*): Terrestrial Plant Test: Seedling, Emergence and Seedling Growth Test

OECD 211: *Daphnia magna* Reproduction Test (freshwater aquatic eco-toxicity test).

OECD 222: Earthworm reproduction test (*Eisenia fetida*).



除非另有书面协议, 本报告由本公司依据《服务通用条款》出具。

《服务通用条款》印刷在正本报告纸背面, 或通过 <http://www.sgs.com/en/Terms-and-Conditions.aspx> 查询, 电子格式文件可通过 <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx> 获取。请特别关注其中涉及责任限定, 赔偿以及司法管辖的相关条款。任何报告的持有方需知悉, 此报告内容仅反映SGS受限于客户指示下, 且在当时所得结论。SGS仅对其客户负责, 并且此报告不能免除交易各方根据交易文件所享有的权利和应履行的义务。未获得本公司书面批准, 本文件不得进行复制, 全文除外。任何未经授权对报告内容及形式进行的修改、伪造或扭曲都是违法行为, 违法者将会被追究法律责任。除非另有声明, 本测试报告所示结果仅涉及受测样品, 此样品只保留30天。

Attention: To check the authenticity of testing /inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

4th Building, No.889, Yishan Road, Xuhui District Shanghai, China 200233 t (86) 400 960 9661 f (86-21) 6115 6899 www.sgs.com.cn
中国·上海·徐汇区宜山路889号4号楼 邮编: 200233 t (86) 400 960 9661 f (86-21) 6115 6899 sgs.china@sgs.com




Research Centre
for Toxic Compounds
in the Environment

2

Conclusion: The trial concluded that the biotransformed plastic products (PP and PE) containing Polymateria's technologies (Cycle+) have met the criteria for all ecotoxicity tests required to reach BS PAS 9017 specification and can thus be considered safe for contact in soil, plant and water environments.

Professor Luděk Bláha
Deputy Director of RECETOX

Signature..... 

In Brno, CZ, on date 30th April, 2021

Stamp:

MASARYKOVA UNIVERZITA
Přirodovědecká fakulta
Centrum pro výzkum
toxických látek v prostředí
Kotlářská 2, 611 37 Brno



除非另有书面协议, 本报告由本公司依据《服务通用条款》出具。

《服务通用条款》印刷在正本报告纸背面, 或通过 <http://www.sgs.com/en/Terms-and-Conditions.aspx> 查询, 电子格式文件可通过 <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx> 获取。请特别关注其中涉及责任限定, 赔偿以及司法管辖的相关条款。任何报告的持有方需知悉, 此报告内容仅反映SGS受限于客户指示下, 且在当时所得结论。SGS仅对其客户负责, 并且此报告不能免除交易各方根据交易文件所享有的权利和应履行的义务。未获得本公司书面批准, 本文件不得进行复制, 全文除外。任何未经授权对报告内容及形式进行的修改、伪造或扭曲都是违法行为, 违法者将会被追究法律责任。除非另有声明, 本测试报告所示结果仅涉及受测试样品, 此样品只保留30天。

Attention: To check the authenticity of testing /inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com


4th Building, No.889, Yishan Road, Xuhui District Shanghai, China 200233 t (86) 400 960 9661 f (86-21) 6115 6899 www.sgs.com.cn
中国·上海·徐汇区宜山路889号4号楼 邮编: 200233 t (86) 400 960 9661 f (86-21) 6115 6899 sgs.china@sgs.com



* The marked activities are not covered by the ENAC accreditation.

TEST CERTIFICATE		Number: AST-21-097-06 Date of tests: 03/02/2022-09/11/2022 Certificate issue: 07/02/2023
COMPANY	POLYMATERIA LTD Imperial College i-Hub White City Campus 80 Wood Lane W120BZ LONDON UNITED KINGDOM	
PETITIONER	Florence Huynh	
PRODUCT NAME	PP_PVM_25072021_559_W - Description: Polypropylene sample from a polypropylene product, containing Polymateria Technology at 2% loading rate (wt%), manufactured by [REDACTED] - Code: AST-21-097-06	
TESTS PERFORMED ACCORDING TO STANDARDS OR INTERNAL PROCEDURES	Determination of the ultimate aerobic biodegradability of plastic materials in soil under controlled soil conditions according to the UNE-EN ISO 17556:2019 standard.	
RESULTS	According to reports: AST-21-097-6-EN/1	

SAMPLE

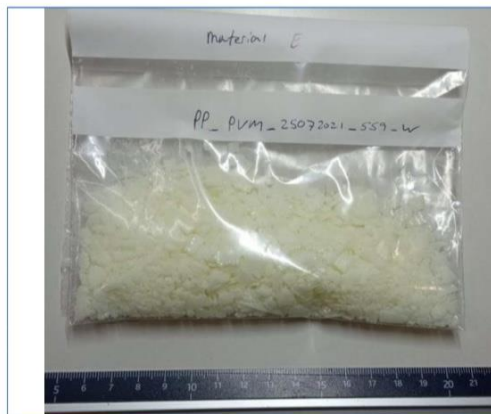

Customer's reference	PP_PVM_25072021_559_W Polypropylene sample from a polypropylene product, containing Polymateria Technology at 2% loading rate (wt%), manufactured by [REDACTED]
AIMPLAS code	AST-21-097-06
Description	Yellowish crushed
Reception date	19/01/2022



TEST CERTIFICATE

Number: AST-21-097-06
Date of tests: 03/02/2022-09/11/2022
Certificate issue: 07/02/2023

Test method

Standard: Determination of the ultimate aerobic biodegradability of plastic materials in soil under controlled soil conditions according to the UNE-EN ISO 17556:2019 standard.

Method: The determination of the aerobic biodegradability of the plastic material samples has been carried out under controlled soil conditions.

The test method used is based on the method reflected in the UNE-EN ISO 17556:2019 standard and is based on the measurement of carbon dioxide generated by gravimetry.

In the present test, the soil used is a standardized soil and the material to be analyzed is tested in a size of 20x20 mm.

2500 mg (dry solids) of sample are mixed with 300 g (dry solids) in each 3-liter capacity reactor and intensively maintained under optimum oxygen conditions, temperature 25 ± 2 ° C and humidity (optimum water content between 40% and 60% of the total water holding capacity) for a test period of six months, extendable to 2 years under specific circumstances.

Air was supplied into the vessels to ensure aerobic conditions throughout the test. Furthermore, the test vessels were subjected to stir twice a week in order that the air distribution was homogeneous throughout the vessel.

The test vessels were distributed as follows:

- Three reactors for the blank (compost).
- Three reactors for reference material (cellulose).
- Three reactors for each test material.

During the aerobic biodegradation of the material, the amount of carbon dioxide generated in each of the reactor is continuously recorded and analyzed by an IR detector and the flow rate is determined by an on-line flowmeter. The percentage of biodegradation is calculated as the ratio of the carbon dioxide generated from the test material to the theoretical maximum amount of carbon dioxide in the test material (ThCO₂).

The amount of carbon dioxide generated is absorbed in a column and measured at intervals of time by weighing the grams of CO₂ retained using a precision electronic scale. The percentage of biodegradation is calculated by the relationship between the carbon dioxide generated from the test material and the maximum theoretical amount of carbon dioxide (ThCO₂) that can be produced from the test material.

Standard: Determination of Total Nitrogen (Nt)^o

Method: - Compost matrix: Internal procedure PI-LTL-6.038.
- Plastic matrix: Internal procedures B-N211 and B-N214 according to ASTM D5291



除非另有书面协议, 本报告由本公司依据《服务通用条款》出具。
《服务通用条款》印刷在正本报告纸背面, 或通过 <http://www.sgs.com/en/Terms-and-Conditions.aspx> 查询, 电子格式文件可通过 <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx> 获取。请特别关注其中涉及责任限定, 赔偿以及司法管辖的相关条款。任何报告的持有方需知悉, 此报告内容仅反映SGS受限于客户指示下, 且在当时所得结论。SGS仅对其客户负责, 并且此报告不能免除交易各方根据交易文件所享有的权利和应履行的义务。未获得本公司书面批准, 本文件不得进行复制, 全文除外。任何未经授权对报告内容及形式进行的修改、伪造或扭曲都是违法行为, 违法者将会被追究法律责任。除非另有声明, 本测试报告所示结果仅涉及受测试样品, 此样品只保留30天。
Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN_Doccheck@sgs.com

4th Building, No.889, Yishan Road, Xuhui District Shanghai, China 200233 t (86) 400 960 9661 f (86-21) 6115 6899 www.sgs.com.cn
中国·上海·徐汇区宜山路889号4号楼 邮编: 200233 t (86) 400 960 9661 f (86-21) 6115 6899 sgs.china@sgs.com

TEST CERTIFICATE

Number: AST-21-097-06
Date of tests: 03/02/2022-09/11/2022
Certificate issue: 07/02/2023

Test method D for matrices: Biomass (wood, pruning residues, sludge, manure, residues from the agricultural, wood and paper industries), solid biofuels and for Petroleum Products

Standard:

Determination of Total Organic Carbon (COT)^d

Method:

- Compost matrix: Internal procedure PI-LTL-6.081 (Oxid. Dichromate)

- Plastic matrix: Internal procedures B-N211 and B-N214 according to ASTM D5291

Test method D for matrices: Biomass (wood, pruning residues, sludge, manure, residues from the agricultural, wood and paper industries), solid biofuels and for Petroleum Products

^c Subcontracted test covered by ENAC accreditation N° 121/LE1782 in compost matrix.

^d Subcontracted test covered by accreditation RvA N° 135 in plastic matrix.

Results

Start date: 03/02/2022
Finish date: 09/11/2022

1) IDENTIFICATION AND CHARACTERIZATION OF PARAMETERS

- **Normalised soil composition**

Table 1

Normalised soil	Theoretical amount (g dry mass/reactor)
Amount of normalized soil/ reactor	200,000
Quartz sand	140,000
Clay	20,000
Natural soil	32,000
Compost	8,000
KH ₂ PO ₄	0,040
MgSO ₄	0,020
NaNO ₃	0,024
Urea	0,012
NH ₄ Cl	0,024



除非另有书面协议, 本报告由本公司依据《服务通用条款》出具。

《服务通用条款》印刷在正本报告纸背面, 或通过 <http://www.sgs.com/en/Terms-and-Conditions.aspx> 查询, 电子格式文件可通过 <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx> 获取。请特别关注其中涉及责任限定, 赔偿以及司法管辖的相关条款。任何报告的持有方需知悉, 此报告内容仅反映SGS受限于客户指示下, 且在当时所得结论。SGS仅对其客户负责, 并且此报告不能免除交易各方根据交易文件所享有的权利和应履行的义务。未获得本公司书面批准, 本文件不得进行复制, 全文除外。任何未经授权对报告内容及形式进行的修改、伪造或扭曲都是违法行为, 违法者将会被追究法律责任。除非另有声明, 本测试报告所示结果仅涉及受测试样品, 此样品只保留30天。

Attention: To check the authenticity of testing /inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN_Doccheck@sgs.com

Building, No.889, Yishan Road, Xuhui District Shanghai, China 200233 t (86) 400 960 9661 f (86-21) 6115 6899 www.sgs.com.cn
中国·上海·徐汇区宜山路889号4号楼 邮编: 200233 t (86) 400 960 9661 f (86-21) 6115 6899 sgs.china@sgs.com

TEST CERTIFICATE

Number: AST-21-097-06
 Date of tests: 03/02/2022-09/11/2022
 Certificate issue: 07/02/2023

2) TEST QUANTITIES

QUANTITY OF CARBON DIOXIDE AND CALCULATION OF THE PERCENT OF BIODEGRADABILITY

The following tables and figures show the evolution of CO₂ production and degree of biodegradation of the vessels containing the blank, the reference material and the test sample, respectively.

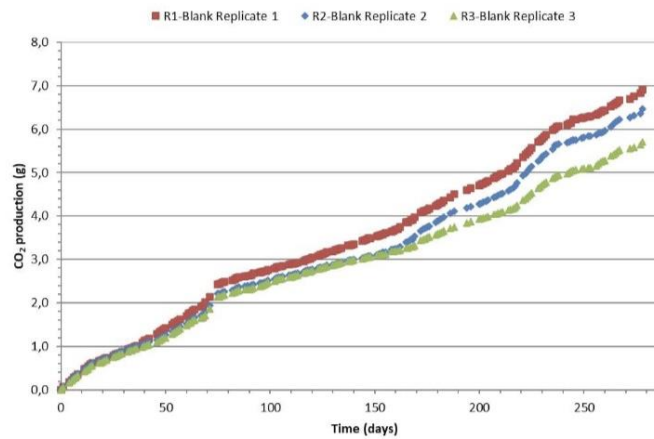


Figure 1. Evolution of CO₂ production (for each replica) of the blank

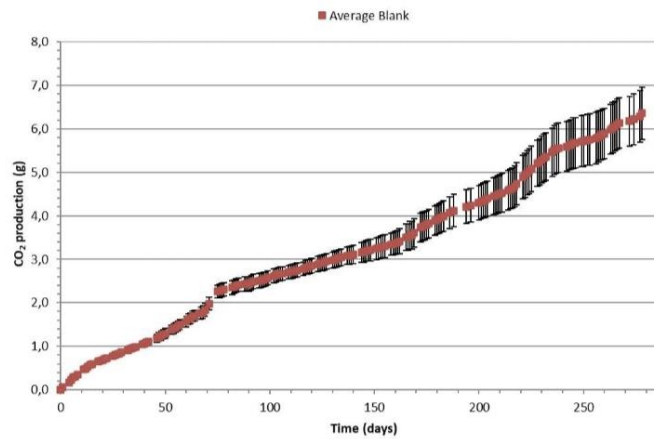


Figure 2. Evolution of CO₂ production (average value) of the blank



TEST CERTIFICATE

Number: AST-21-097-06
 Date of tests: 03/02/2022-09/11/2022
 Certificate issue: 07/02/2023

• **Reference (cellulose) results**

The graphical evolution of CO₂ production and the percentage of biodegradation (for each replica) and the average percentage of biodegradation of the reference material are shown below:

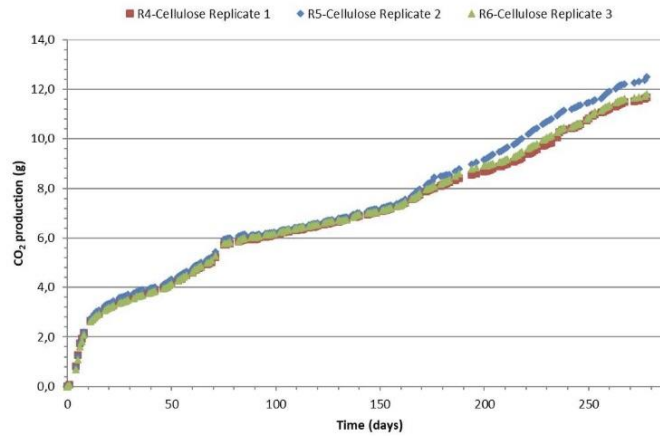


Figure 3. Evolution of CO₂ production (for each replica) of the reference material (cellulose)

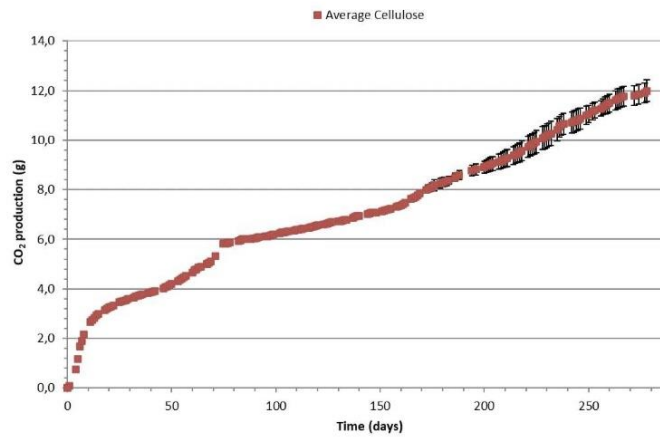


Figure 4. Evolution of CO₂ production (average value) of the reference material (cellulose)



TEST CERTIFICATE

Number: AST-21-097-06
 Date of tests: 03/02/2022-09/11/2022
 Certificate issue: 07/02/2023

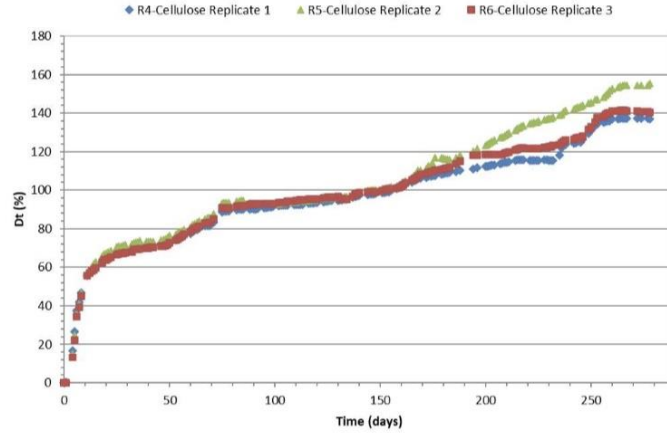


Figure 5. Evolution of the percentage of biodegradation (for each replica) of the reference material (cellulose)

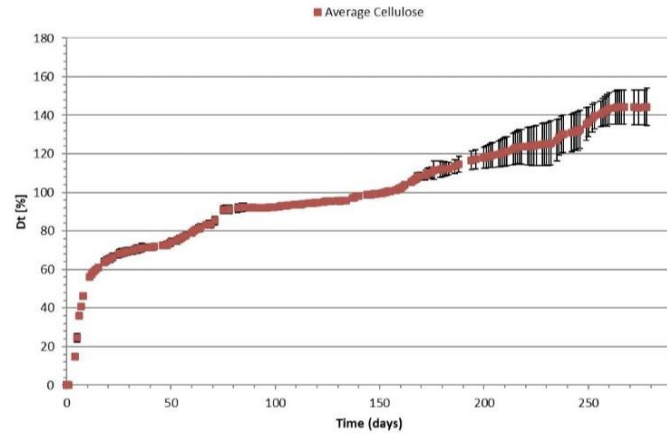


Figure 6. Evolution of the percentage of biodegradation (average value) of the reference material (cellulose)



除非另有书面协议, 本报告由本公司依据《服务通用条款》出具。
 《服务通用条款》印刷在正本报告纸背面, 或通过 <http://www.sgs.com/en/Terms-and-Conditions.aspx> 查询, 电子格式文件可通过 <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx> 获取。请特别关注其中涉及责任限定, 赔偿以及司法管辖的相关条款。任何报告的持有方需知悉, 此报告内容仅反映SGS受限于客户指示下, 且在当时所得结论。SGS仅对其客户负责, 并且此报告不能免除交易各方根据交易文件所享有的权利和应履行的义务。未获得本公司书面批准, 本文件不得进行复制, 全文除外。任何未经授权对报告内容及形式进行的修改、伪造或扭曲都是违法行为, 违法者将会被追究法律责任。除非另有声明, 本测试报告所示结果仅涉及受测试样品, 此样品只保留30天。
 Attention: To check the authenticity of testing /inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com
 4th Building, No.889, Yishan Road, Xuhui District Shanghai, China 200233 t (86) 400 960 9661 f (86-21) 6115 6899 www.sgs.com.cn
 中国·上海·徐汇区宜山路889号4号楼 邮编: 200233 t (86) 400 960 9661 f (86-21) 6115 6899 sgs.china@sgs.com

TEST CERTIFICATE

Number: AST-21-097-06
 Date of tests: 03/02/2022-09/11/2022
 Certificate issue: 07/02/2023

• **Results sample AST-21-097-06**

The graphical evolution of CO₂ production and the percentage of biodegradation (for each replica) and the average percentage of biodegradation of the reference material are shown below:

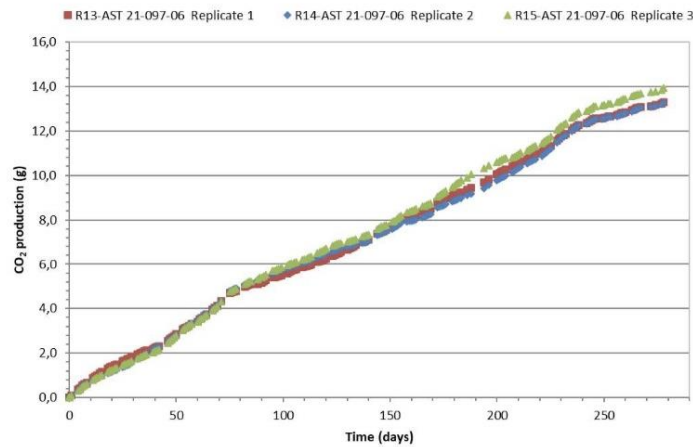


Figure 7. Evolution of CO₂ production (for each replica) of sample AST-21-097-06

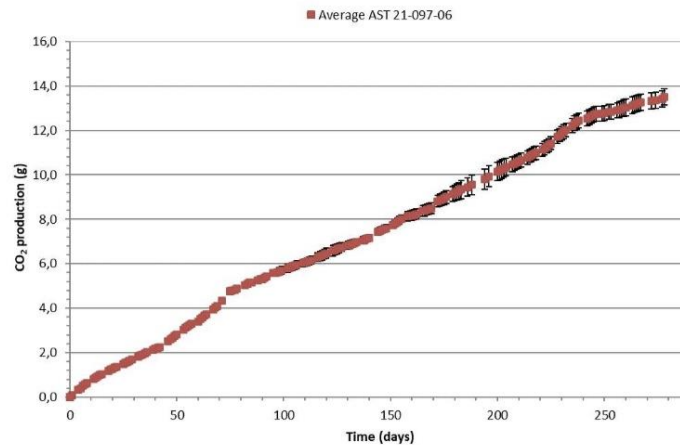


Figure 8. Evolution of CO₂ production (average value) of sample AST-21-097-06



TEST CERTIFICATE

Number: AST-21-097-06
 Date of tests: 03/02/2022-09/11/2022
 Certificate issue: 07/02/2023

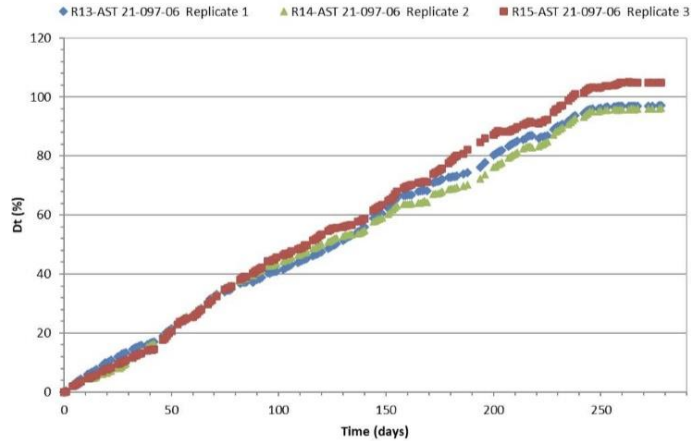


Figure 9. Evolution of the percentage of biodegradation (for each replica) of sample AST-21-097-06

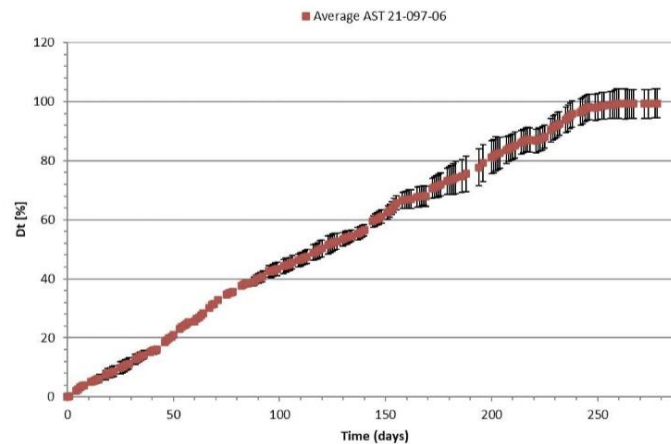


Figure 10. Evolution of the percentage of biodegradation (average value) of sample AST-21-097-06



除非另有书面协议, 本报告由本公司依据《服务通用条款》出具。

《服务通用条款》印刷在正本报告纸背面, 或通过 <http://www.sgs.com/en/Terms-and-Conditions.aspx> 查询, 电子格式文件可通过 <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx> 获取。请特别关注其中涉及责任限定, 赔偿以及司法管辖的相关条款。任何报告的持有方需知悉, 此报告内容仅反映SGS受限于客户指示下, 且在当时所得结论。SGS仅对其客户负责, 并且此报告不能免除交易各方根据交易文件所享有的权利和应履行的义务。未获得本公司书面批准, 本文件不得进行复制, 全文除外。任何未经授权对报告内容及形式进行的修改、伪造或扭曲都是违法行为, 违法者将会被追究法律责任。除非另有声明, 本测试报告所示结果仅涉及受测试样品, 此样品只保留30天。

Attention: To check the authenticity of testing /inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN_Doccheck@sgs.com

4th Building, No.889, Yishan Road, Xuhui District Shanghai, China 200233 t (86) 400 960 9661 f (86-21) 6115 6899 www.sgs.com.cn
 中国·上海·徐汇区宜山路889号4号楼 邮编: 200233 t (86) 400 960 9661 f (86-21) 6115 6899 sgs.china@sgs.com

TEST CERTIFICATE

Number: AST-21-097-06
 Date of tests: 03/02/2022-09/11/2022
 Certificate issue: 07/02/2023

3) MAINTENANCE OPERATIONS CARRIED OUT DURING THE TEST AND AT THE END OF THE TEST

- Temperature control during the test
- Humidity control and other maintenance operations during the test

Water is added to each reactor during the stirring process to maintain the total weight of the reactors, and thus, to maintain the optimum humidity in the mixture.

- pH control

4) VALIDITY OF THE TEST

In accordance with the UNE-EN ISO 17556:2019 standard, the test is considered valid if the following criteria are met:

- (a) The degree of biodegradation of the reference material is greater than 60% in the plateau phase or at the end of the test.
- (b) The DBO or carbon dioxide in three blanks are at 20% in the plateau phase or at the end of the test.



除非另有书面协议, 本报告由本公司依据《服务通用条款》出具。
 《服务通用条款》印刷在正本报告纸背面, 或通过 <http://www.sgs.com/en/Terms-and-Conditions.aspx> 查询, 电子格式文件可通过 <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx> 获取。请特别关注其中涉及责任限定, 赔偿以及司法管辖的相关条款。任何报告的持有方需知悉, 此报告内容仅反映SGS受限于客户指示下, 且在当时所得结论。SGS仅对其客户负责, 并且此报告不能免除交易各方根据交易文件所享有的权利和应履行的义务。未获得本公司书面批准, 本文件不得进行复制, 全文除外。任何未经授权对报告内容及形式进行的修改、伪造或扭曲都是违法行为, 违法者将会被追究法律责任。除非另有声明, 本测试报告所示结果仅涉及受测试样品, 此样品只保留30天。
 Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com
 4th Building, No.889, Yishan Road, Xuhui District Shanghai, China 200233 t (86) 400 960 9661 f (86-21) 6115 6899 www.sgs.com.cn
 中国·上海·徐汇区宜山路889号4号楼 邮编: 200233 t (86) 400 960 9661 f (86-21) 6115 6899 sgs.china@sgs.com

TEST CERTIFICATE	Number: AST-21-097-06
	Date of tests: 03/02/2022-09/11/2022
	Certificate issue: 07/02/2023

*** CONCLUSIONS**

Determination of the ultimate aerobic biodegradability of plastic materials in soil under controlled soil conditions according to the UNE-EN ISO 17556:2019 standard.

The percentage of biodegradation average value of the samples after 278 days of testing, is shown in the following table:

Sample	D _{tm} (%) 278 days
AST-21-097-06	99,40
Standard requirement	>90%

To demonstrate that a product is biodegradable under controlled soil conditions according to this standard, 90% biodegradation has to be achieved within a minimum of 6 months and a maximum of 24 months.

Electronic signature of the authorized signatories:

NEUS|SORIANO|MARCO
Material Characterization & Testing Group Leader
2023.02.08 12:04:02 +01'00'



Valencia Parc Tecnològic	Tel.: +34 96 136 60 40
Calle Gustave Eiffel, 4	Fax: +34 96 136 60 41
Apartado de correos 51	http://www.aimplas.es
46980 PATERNA Valencia - España	email: info@aimplas.es

*** 报告结束 ***



除非另有书面协议, 本报告由本公司依据《服务通用条款》出具。
《服务通用条款》印刷在正本报告纸背面, 或通过 <http://www.sgs.com/en/Terms-and-Conditions.aspx> 查询, 电子格式文件可通过 <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx> 获取。请特别关注其中涉及责任限定, 赔偿以及司法管辖的相关条款。任何报告的持有方需知悉, 此报告内容仅反映SGS受限于客户指示下, 且在当时所得结论。SGS仅对其客户负责, 并且此报告不能免除交易各方根据交易文件所享有的权利和应履行的义务。未获得本公司书面批准, 本文件不得进行复制, 全文除外。任何未经授权对报告内容及形式进行的修改、伪造或扭曲都是违法行为, 违法者将会被追究法律责任。除非另有声明, 本测试报告所示结果仅涉及受测试样品, 此样品只保留30天。
Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN_Doccheck@sgs.com

4 th Building, No.889, Yishan Road, Xuhui District Shanghai, China 200233	t (86) 400 960 9661	f (86-21) 6115 6899	www.sgs.com.cn
中国·上海·徐汇区宜山路889号4号楼 邮编: 200233	t (86) 400 960 9661	f (86-21) 6115 6899	sgs.china@sgs.com